

## Extreme Burden Conduct Of Steel Shafts With Web Openings

<sup>1</sup>R Jaipal Assistant Professor [jaipalcivil.jntu@gmail.com](mailto:jaipalcivil.jntu@gmail.com)  
<sup>2</sup>M.PRIYAMVADHA Assistant Professor [priyam.sri.157@gmail.com](mailto:priyam.sri.157@gmail.com)  
Department of Civil Engineering,  
Pallavi Engineering College Hyderabad, Telangana 501505.

### ABSTRACT

The paper also includes an examination of the ultimate load behavior of steel beams having web holes. ISMB 100 hot rolled steel beams with web holes have seen a great deal of testing. Because of this, there was a concentrated load placed on the center of the beams' span. Research on the failure of these particular beams was comprehensive in order to determine the optimal ratio of aperture span to diameter. Conventional finite-element analysis software, such as ANSYS, was used to study all the beams and the findings were compared to those acquired via test. There is a direct correlation between opening size and carrying capacity, according to the testing findings. The simulation and experiment findings are in excellent accord. In the parametric analysis, the ideal placement for the web opening is in the center two-thirds of the span.

### 1. Introduction

For the first time in structures during World War II, open web expanded steel beams were used to reduce steel construction costs. These beams were selected by the designers in order to improve the original beam's stiffness and strength. One section of the root beam web is cut to a certain shape before being joined with another piece by welding. Consequently, the entire beam depth grows, increasing the original section's capacity by a factor of two. For decades, structural engineers have sought for castellated beams' excellent strength to weight ratio in their drive to produce lighter and more cost-effective steel structures.

Currently, the design principles and criteria for these beams are either inadequate or difficult to implement (2009). Because the I-Beam behavior with web apertures is difficult to understand and evaluate, simulating the design process has proven problematic. This means that further study is needed to collect enough data to provide a clear design strategy. Few experimental and analytical studies have been conducted on steel beams with web holes until this point. Using Redwood's proposed equivalent rectangular hole with altered proportions for steel beams with circular web apertures, the bulk of the design criteria are still appropriate (1969). Steel beams might be overestimated due to a simple loading method. According to

the elasticity theory and curved beam analysis, Chan and Redwood (1974) investigated the elastic stress distribution in beams with wide circular web apertures. Olander's study on steel beam load-carrying capability with multiple circular web holes provided the basis for this diagram, which was developed in 1990 at the Steel Construction Institute (1953).

After minor tweaks in 1998, the technique was included into Eurocode 3 Amendment A2: Part 1.1: Annex N as an entirely new section. With independent circular web holes, Annex N provides a new set of approximate design requirements.

Steel beams with circular and rectangular perforations were explored experimentally and statistically by Thevendran and Shanmugan (1991) of Tamil Nadu. Plexiglass sheets were utilized to construct models with cantilever beams and ease of support. The buckling load of this kind of beam may be computed using an energy method. Chung and Lawson (2001) used a Eurocode 4 design technique for composite bars with large web apertures to concentrate steel radiates with round and rectangular gaps. A precise shear-second connection bend developed by Chung, Liu, and Ko (2001) was used to get our results.

Against the vierendeel method, a pierced area and configuration technique for steel uses round web gaps. Chung, Liu, and Ko (2003) developed a precise technique for manufacturing steel radiates with web apertures of various sizes and shapes using a summarized second shear connection bend. Detailed explanations and real-world examples are provided in this article. The analysts were able to calculate a definite vertical shear load strength of web-posts constructed from specified web opening shapes using the precise approach devised by Tsavdaridis and D'Mello (2011). A thorough assessment was carried out by Mukhda and Gupta, both in terms of the test and the investigation. As part of the evaluation, the first is tested for dissatisfaction and its size and form are evaluated.

The impartial zone over the range of the bar that should be welcomed firmly without web post disappointment is excluded from data on radiates with web gaps. In addition to an evaluation of the unbiased zone inside their range, these steel radiates are designed with web gaps that modify the proportion of dividing to the width of the apertures they open up. Such beams are studied in this study, with results from finite-element analysis being contrasted to those from experiments (2009). This investigation has a dual emphasis. Finite element

solutions for web-holed steel beams are calibrated with the experimental data. The results of these studies may help provide information on the overall behavior of these beams, as well. These beams are subject to shear failure in the web post. In this study, failure mechanisms, load-deflection behavior, and ultimate load-carrying capacity are taken into consideration.

## 2. Experimental investigation

### *Details of test specimens*

Five different spacing-to-diameter ratios of steel beams with web apertures were tested to failure: 1.07, 1.33, 1.5, 2.0, and 3.0 (defined as the ratio of the center-to-center distance of openings to the diameter of openings,  $S/D_o$ ). Other criteria include the position of the stiffener and its geometrical dimensions. As can be seen in Figure 1, there are many distinct geometrical characteristics and loading arrangements for the beams. Experimentation is shown in Figure 2.

### *Fabrication of the test specimens*

All test specimens were constructed using hot rolled steel beams of Grade E250 (Fe410W) that corresponds to IS:2062(2011). Making the part was done in accordance with how it is represented in Figure 1. On a web plate, precise holes were drilled out of the material using drilling techniques that needed great care and precision. Due to the heating process, welding was completely ruled out as a method for creating openings in steel. Stiffeners were welded onto both sides of the web plate after all of the web plate slots were cut out. The weld distortion in the web plate was kept to a minimum thanks to extra attention. Using lime, the specimens were whitewashed in order to accurately distinguish the yielding and stress-concentration zones. The dried lime from the sections falls to the ground when the yielding occurs, making it simpler to locate the area of highest stress.


### *Material properties*

Section segments' flange and web plate tensile test coupons were cut to determine the mechanical properties required for the modeling procedure. Test specimens from both flange and web sections were utilized for the material testing, along with those from all other sections. Their performance was evaluated at the testing facility using a universal

testing machine with a capacity of 500 kN. Using coupon tests, we were able to collect the following data: yield pressure, ultimate pressure, and modulus of elasticity (see Table 1).

### 3. Finite-element analysis

The ultimate load bearing capability of the cellular beams used in the experiment will be compared using a non-linear finite element analysis in this section (FEA). As the external stress level increases, the finite-element method is applied in an attempt to anticipate their total reaction. Analysis of experimental data and investigation of nonlinear behavior of failure modes such as shear buckling and vierendeel bending of web-holed steel beams are carried out using FEMs. To develop a 3D finite element model of steel beams with I-shaped web holes, ANSYS v12 elasto-plastic finite element software was used (2009). Despite the apparent defects in the geometry of the specimens used in experiments, faultless copies of these specimens were made for use in modeling. Bilinear stress-strain curves were integrated with the von Mises yield criterion and the kinematic hardening rule as a steel material model. The large deformation effect has

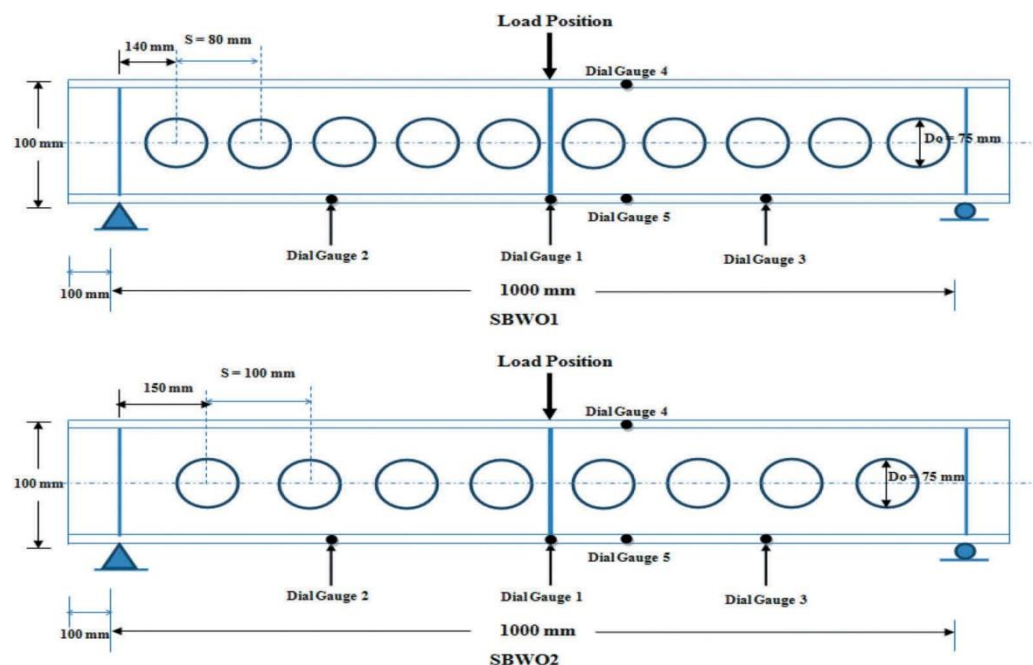

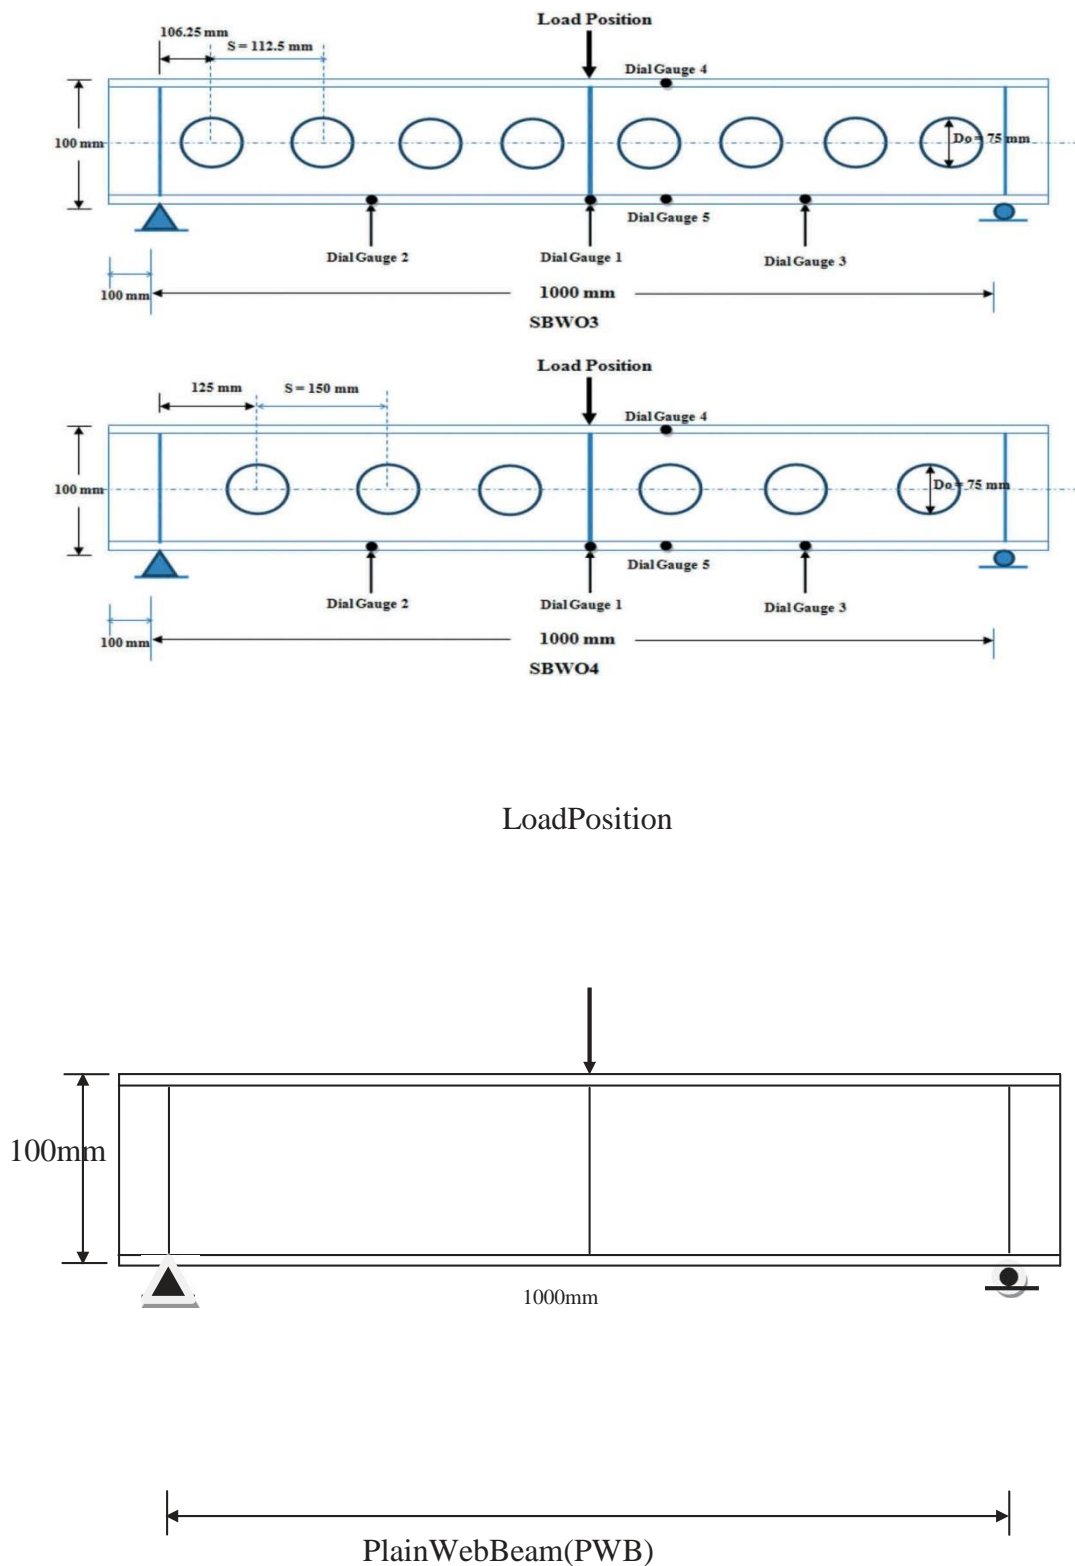


Figure1. Geometrical details of steel beams with web openings.


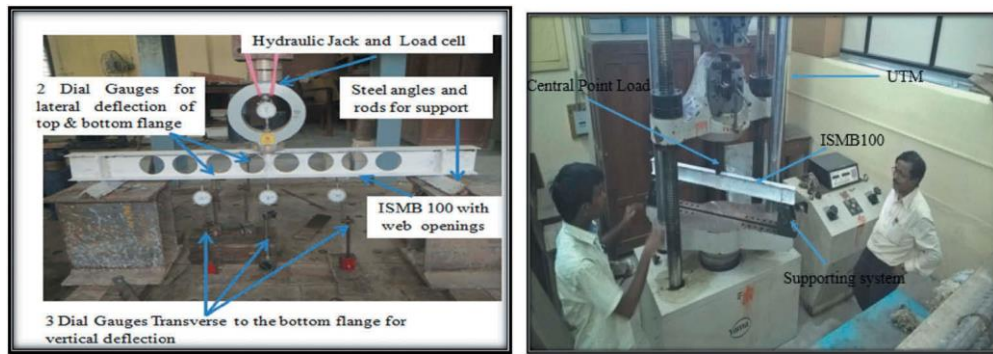


Figure 2. Typical view of the test setup.

Torsion and warping rigidities of unbraced beams may be estimated using the length and minor moment of inertia in the cross-section of the beams. Convergence study yielded quantifiable results.

The coupon tests yielded material attributes (Table 1) that were employed in the convergence research. Vertical, lateral, and horizontal displacements are all included.

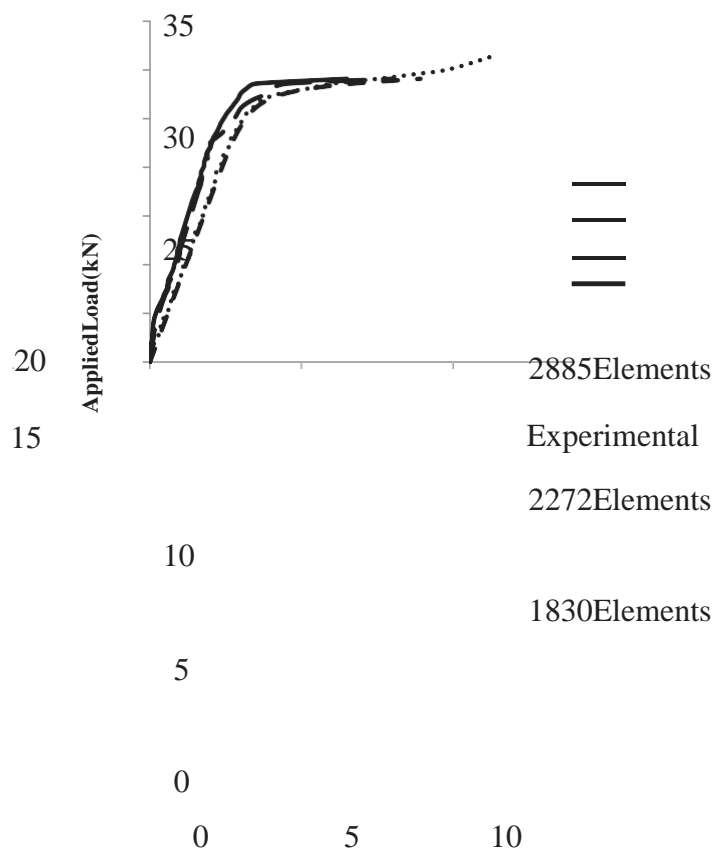

### **Mid-Span Displacement(mm)**

Figure 4. Convergence study on the steel beam with web openings SBWO2.

The buckling mode determined from the elastic stage was imposed in the steel beam's final analysis using web apertures. As a result, a suitable finite element model was found for the second steel beam with web apertures after convergence experiments were performed. Experiments on three mesh designs of 1830, 2272 and 2885 components have been shown in Figure 4. 1830 against 2275 components had an ultimate strength differential of roughly 5%, whereas the difference between 2275 and 2885 components had a difference of around 2.5%. There was essentially no difference between the load–deflection curves for the 2885-element models and the actual research, as shown in Figure 4. All steel girders with web holes were subjected to finite-element analysis, which had 2885 elements in total. Failure modes were found to be consistent across all of the incidents studied.

#### 4. Results and discussion

Table 3 summarizes the results of experiments and finite element analysis (FEA). Examples of common beams' vertical deflection as a function of applied loads are shown in Figures 5–10. As opening area increases ( $S/D_o$ ), so does the beam stiffness and maximum load, as shown experimentally. Analytical forecasts also underestimate the beam's load-carrying capability. As a result, steel beams with web holes and an ANSYS analysis can accurately predict their ultimate strength. For the most part, the experimental and finite-element findings do not agree with the SBWO1 curve (steel beam with web openings-specimen1). A possible explanation for the disparity in the curves is that the ANSYS software is incapable of handling the data. For SBWO1 and SBWO2, the distorted forms shown in Figures 11 and 12 were obtained by experimental and finite-element analysis.

#### 5. Investigation of neutral zone in steel beam with web openings

Steel beams with web holes were subject to a parametric investigation after the finite-element method was shown to be accurate in terms of ultimate load-carrying capability. Container opening standards have been simplified by British Standards Institution (1998) and the Canadian Standard AISC-LRFD, for instance.




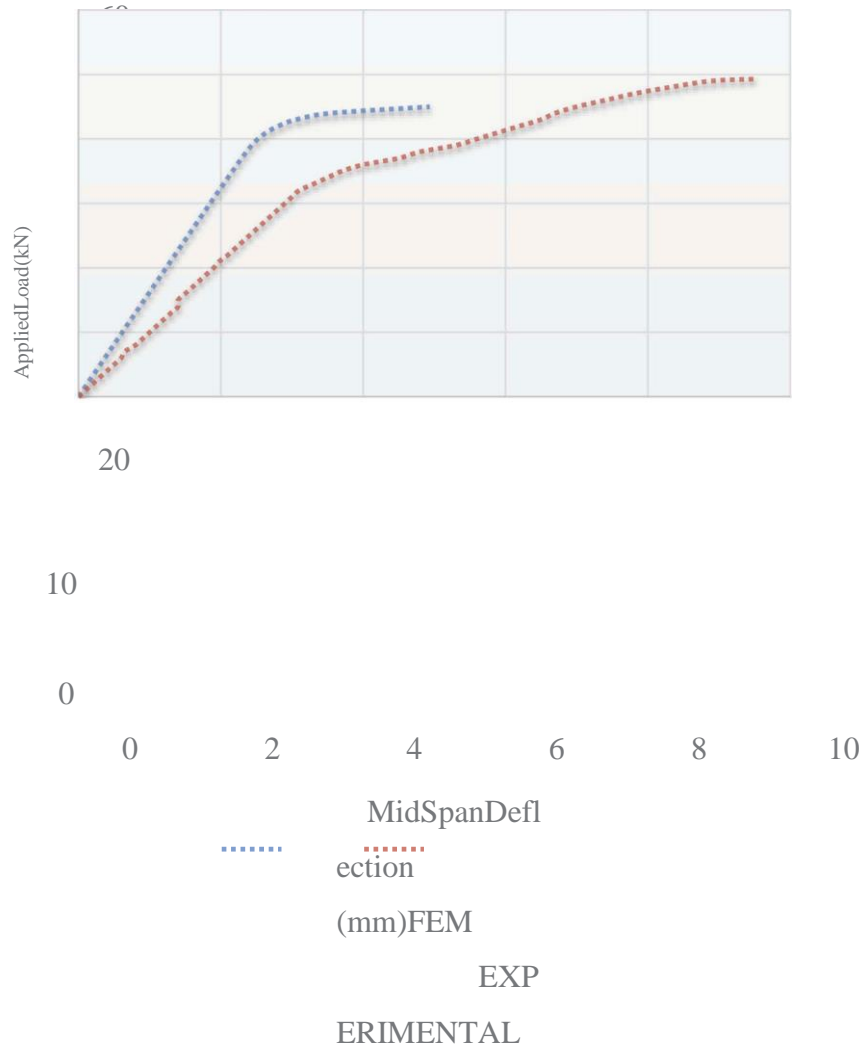


Figure10.

Loadvs.deflectioncurveforsolidwebbeam.



(a)

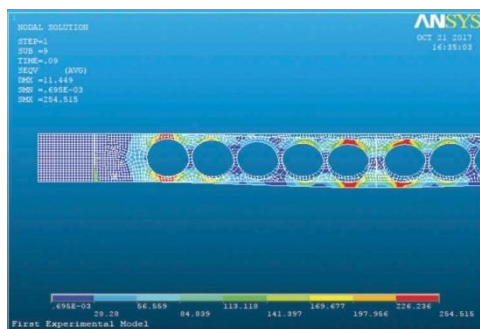

(b)

Figure 11. Deformed shape of the beam SBWO1 (a) FEM and (b) experimental.

make it such that the beam does not crack or break. These regulations, however, are very conservative because of the wide range of options they provide, and they generally restrict openings to three-quarters of the depth and two-thirds of the width of the beam. The fixation of a few criteria might lead to more adaptable and cost-effective solutions under typical construction settings. By using concentric holes of same size and shape, beam strength is not affected. You can construct web openings without reference to beam net section if you know where the neutral zone is. As a result, the usage of analytical calculation techniques has become unnecessary. To easily determine the neutral zone depth ( $h_{nz}$ ), which is two times the web opening half-depth plus opening eccentricity, consider its symmetrical placement in relation to the steel section centroid. By aligning the apertures such that they are symmetrical with regard to the steel section centroid, you can see the opening depth  $h_{nz}$  (concentric opening). Concentrated pressures were applied to a 5-meter-long ISMB400 section with several openings. 0.5, 0.62, and 0.75 D-diameter holes are among the ones studied in this investigation (where D is the diameter of openings). To improve the quality of a web post, the spacing-to-diameter ratio (S/Do) and location of the apertures are critical. Figures 13–15 indicate that the load–deflection response of the beam is almost equal to that of the plain-web beam for apertures between 2L and 3L, as shown in the parametric experiment.

## 6. Conclusions

In this study, the results of experiments on steel beams having web apertures are discussed. Various beams with various web opening arrangements have been put to the test to the point of deflation.

- S/Do was determined to have a minimum limit of 1.08, which was deemed to be essential.
- Researchers discovered that a S/Do ratio of between 1.33 and 1.5 was very effective.
- The beam's response is almost equal to that of a plain-web beam when the apertures are provided in this ratio.
- The most common failure mechanism seen in experimental studies is web post buckling failure.
- When a Vierendeel mechanism fails, four plastic hinges develop at the corners of the

aperture. This is the most typical failure scenario.

- It is also clear that the finite-element analysis findings and the results from the trials are in excellent accord.
- When designing the apertures, keep in mind that bending is more important than shear when determining where to place them.

## References

1. Altifillisch, M. D., B. R. Cooke, and A. A. Toprac. 1957. "An Investigation of Open Web-Expanded Beams." *Weld Research Council Bulletin* 47:77–88.
2. ANSYS version 12.0, Inc. 2009. Canonsburg, PA.
3. Bazile, A., and J. Texier. 1968. "Test on Castellated Beams' Constr Metallique." 1(3):12–25.
4. BSI (British Standards Institution). 1998. "European Committee for Standardization." *ENI 993-1-3, Eurocode 3 (EC3): Design of steel structures- Part 1.1: general rules and rules for buildings; 1992, and Amendment A2 of Eurocode 3: Annex N 'Openings in webs'*.
5. Chan, P. W., and R. G. Redwood. 1974. "Stresses in Beams with Circular Eccentric Web Holes." *Journal of Structural Division, Proceedings ASCE* 100(ST1):231–248.
6. Chung, K. F., and R. M. Lawson. 2001. "Simplified Design of Composite Beams with Large Web Openings to EuroCode 4." *Journal of Constructional Steel Research* 57:135–163. doi:10.1016/S0143-974X(00)00011-0.
7. Chung, K. F., T. C. H. Liu, and A. C. H. Ko. 2001.
8. "Investigation on Vierendeel Mechanism in Steel Beams with Circular Web Openings." *Journal of Constructional Steel Research* 57: 467–490. doi:10.1016/S0143-974X(00)00035-3.
9. Chung, K. F., T. C. H. Liu, and A. C. H. Ko. 2003. "Steel Beams with Large Web Openings of Various Shapes and Sizes: An Empirical Design Method Using a Generalized Moment-Shear Interaction Curve." *Journal of Constructional Steel Research* 59:1177–1200. doi:10.1016/S0143-974X(03)00029-4.
10. Galambos, A. R., M. U. Husain, and W. G. Spin. 1975. "Optimum Expansion Ratio

- of Castellated Steel Beams.”*Engineering Optimization*1:213–225.doi:10.1080/03052157508960588.
11. 03052157508960588.
12. Husain, M. U., and W. G. Speirs. 1971. “Failure of Castellated Beams Due to Rupture of Welded Joints.” *Acier-Stahl-Steel*.
13. Husain, M. U., and W. G. Speirs. 1973. “Experiments on Castellated Steel Beams.” *Journal of American Weld Society Weld Research Supp*52(8): 329–3423.